

Suppression of Magnetic Order by Pressure in BaFe_2As_2

Hideto Fukazawa*, Nao Takeshita¹,
Takehiro Yamazaki, Kenji Kondo, Kenji Hirayama,
Yoh Kohori, Kiichi Miyazawa^{1,2}, Hijiri Kito¹,
Hiroshi Eisaki¹, and Akira Iyo¹

Department of Physics, Chiba University, Chiba 263-8522

¹*Nanoelectronics Research Institute, National Institute of
Advanced Industrial Science and Technology, Tsukuba
305-8562*

²*Department of Applied Electronics, Tokyo University of
Science, Noda 278-8510*

(Received August 5, 2008)

KEYWORDS: BaFe_2As_2 , magnetic transition, superconductivity, high pressure, nuclear magnetic resonance

The discovery of superconductivity in F-doped $\text{LaFeAsO}^{1)}$ has accelerated further investigations of the related superconductors.²⁻⁴⁾ The common feature of these compounds is the possession of a FeAs layer which is analogous to the CuO_2 plane in high-superconducting-transition-temperature (high- T_c) cuprates. Soon after the intensive investigations of the oxypnictides, the oxygen-free iron pnictide $\text{BaFe}_2\text{As}_2^{5)}$ was proposed as the next candidate parent material of superconductor with high T_c . The crystal structure of this pnictide is the ThCr_2Si_2 -type structure and possesses a similar FeAs layer to that realized in LaFeAsO . Moreover, this material exhibits spin density wave (SDW) anomaly at $T_{\text{SDW}} = 140$ K (BaFe_2As_2).^{5,6)} It is important to note that the compound exhibits structural phase transition from tetragonal ($I4/mmm$) to orthorhombic ($Fmmm$) as well as SDW anomaly.^{5,6)} The most striking feature of this compound is that the SDW anomaly disappears and the superconductivity indeed sets in by hole doping, for example, K substitution for Ba.⁷⁾ In addition, the pressure P induced superconductivity in BaFe_2As_2 was recently reported by the magnetic susceptibility measurements under pressure up to about 6 GPa.⁸⁾ Although it should be revealed by additional experimental approaches whether this superconductivity is intrinsic or not, it is clear that the investigation of this compound under pressure is quite important. In order to understand the relation between the SDW instability and expected superconductivity in BaFe_2As_2 , we performed resistivity ρ measurements and zero-external-field (ZF) ^{75}As nuclear-magnetic-resonance (NMR) measurements of BaFe_2As_2 under high pressure.

In our previous letter, we reported the ^{75}As -NMR spectra of BaFe_2As_2 at various temperatures and the temperature T dependence of the spin-lattice relaxation rate $1/T_1$ of ^{75}As under ambient pressure.⁹⁾ ^{75}As -NMR spectra clearly revealed that magnetic transition occurs at around 131 K in our samples, which corresponds to the emergence of spin density wave. The T dependence of the internal magnetic field H_{int} suggested that the tran-

sition is likely of the first order. We also deduced from the difference of the linewidth of the highly oriented powder and partially oriented powder that the H_{int} at the As site is parallel to c -axis. The steep decrease in $1/T_1$ below T_{SDW} was observed and was due to the gap formation of the SDW at part of the Fermi surface. $1/T_1$ below about 100 K was nearly proportional to T which indicates the relaxation due to the remaining conduction electron at the Fermi level even below T_{SDW} . In our previous paper, we also reported a ZF ^{75}As -NMR spectrum at 1.5 K.^{9,10)} The ZF ^{75}As -NMR spectrum clearly revealed that the magnetically ordered state of this compound is commensurate. Furthermore, the center line of the ZF ^{75}As -NMR spectrum is a good measure of the H_{int} at the As site.

The polycrystalline BaFe_2As_2 was synthesized by a high-temperature and high-pressure method. The samples were confirmed to be nearly single phase by X-ray diffraction analysis. The electrical resistivity was measured by means of ordinary dc four probe method. Cubic anvil apparatus for low temperature measurement¹¹⁾ was used for the resistivity measurements under P up to 13 GPa. Detailed condition for the use of this apparatus is given elsewhere.³⁾ The NMR experiment on the ^{75}As nucleus ($I = 3/2$, $\gamma = 7.292$ MHz/T) was carried out using a phase-coherent pulsed NMR spectrometer. The samples were crushed into powder for use in the experiment. The CuBe-NiCrAl hybrid piston-cylinder cell was used for the NMR measurements under P up to about 2.5 GPa. Daphne 7373 was used for the pressure transmitting medium, which was confirmed to be suited for the measurements under P with the use of the piston cylinder cell.¹³⁾ The pressure and its homogeneity was determined from the nuclear quadrupole resonance frequency and full width at half maximum of ^{63}Cu of Cu_2O at 4.2 K, respectively.¹⁴⁾

In Fig. 1, we show the T dependence of ρ of BaFe_2As_2 under various pressures. ρ exhibits metallic behavior in almost all the T range at all the pressures. At ambient pressure, ρ rapidly decreases below about 131 K ($= T_{\text{SDW}}$).¹²⁾ This is due to SDW anomaly as well as the structural phase transition. The T_{SDW} of our samples is slightly lower than those reported by Rotter *et al.*⁵⁾ and Huang *et al.*⁶⁾ This anomaly apparently becomes broader above 1 GPa: it becomes difficult to determine the SDW and/or structural transition temperature. In the inset of Fig. 1, we show the T dependence of $d\rho/dT$ of BaFe_2As_2 at 2.0 GPa. The large peak can be seen at around 114 K. Because the ρ decreases more steeply below this temperature, which can be interpreted as the suppression of the magnetic scattering, this anomaly is attributable to SDW transition. Hence, we express the characteristic temperature of this anomaly under pressure with T_{SDW} as well as the ambient T_{SDW} . Gradual decrease of ρ at the temperatures above T_{SDW} might be due to the preceding behavior of SDW anomaly.

More clear change in ρ is steep decrease below about 20-30 K under P above 3.0 GPa. This anomaly corresponds to superconducting phase transition which was reported by the magnetic susceptibility measurements under P up to about 6 GPa.⁸⁾ However, we should note that we obtained no zero-resistivity at every pressure.

*E-mail address: hideto@nmr.s.chiba-u.ac.jp

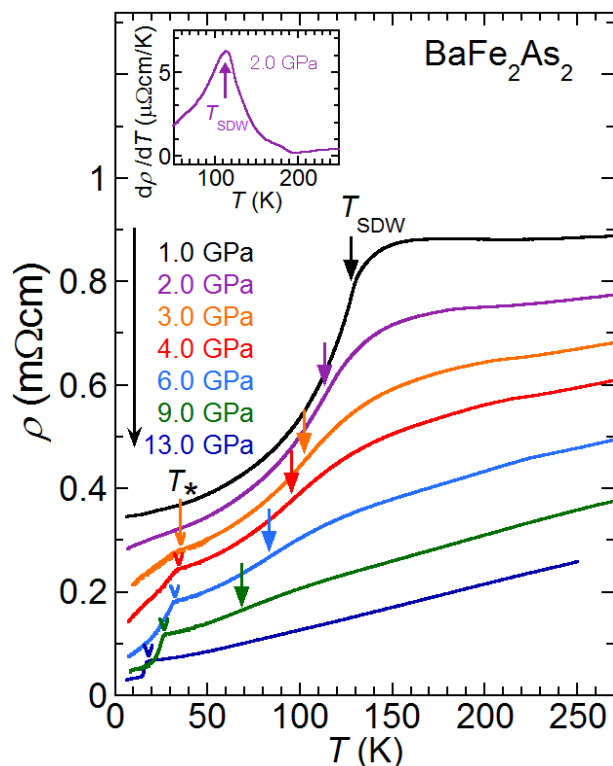


Fig. 1. (Color online) Temperature T dependence of the dc resistivity ρ of BaFe_2As_2 under various pressures. The inset shows the T dependence of $d\rho/dT$ of BaFe_2As_2 at 2.0 GPa.

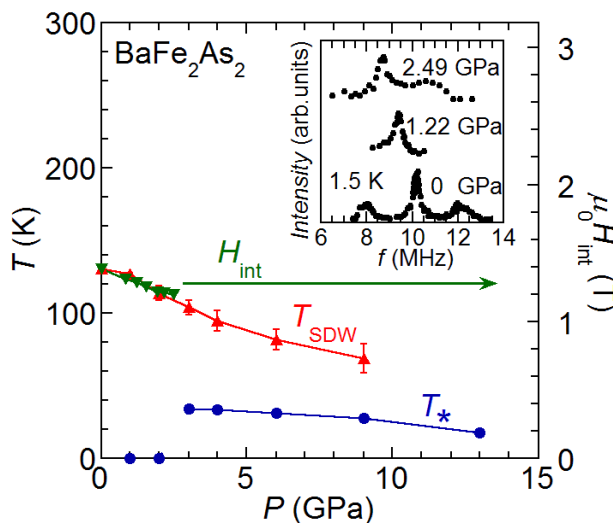


Fig. 2. (Color online) The T - P phase diagram of BaFe_2As_2 determined from resistivity anomalies. Squares (T_{anom}), up triangles (T_{SDW}), and circles (T_*) denote structural-like, SDW, and SC-like transition, respectively. Down triangles denote the internal magnetic fields H_{int} at the As site evaluated from the ZF ^{75}As -NMR measurements at 1.5 K. The inset shows the ZF ^{75}As -NMR spectra at various pressures.

We confirmed its reproducibility with different batches of samples. Simultaneously, we obtained current dependence of the ρ below these temperatures. Therefore, this anomaly is related with superconductivity, but we could not conclude that this anomaly is an intrinsic property of BaFe_2As_2 under pressure. Then, we express the char-

acteristic temperature of this anomaly with T_* .

In Fig. 2, we show the T - P phase diagram of BaFe_2As_2 determined from resistivity anomalies. We also show the P dependence of the H_{int} up to about 2.5 GPa. The H_{int} at the As site was evaluated from the P -dependent center line of the ZF ^{75}As -NMR spectrum as shown in the inset of Fig. 2. Detailed analysis of the spectra to evaluate the H_{int} is written elsewhere.¹⁰⁾ We also show higher satellite line at 2.49 GPa in the inset of Fig. 2 in order to show that the peak at around 8.7 MHz is indeed a center line of the ZF NMR spectrum. The P dependence of the H_{int} is nearly proportional to that of T_{SDW} . This supports that our estimation of the T_{SDW} from ρ is adequate. The phase diagram clearly shows that the SDW anomaly is suppressed by applied P , but is simultaneously quite robust against P . Furthermore, if T_* is an intrinsic T_c of BaFe_2As_2 , this phase diagram suggests the possibility of coexistence of SDW ordered phase and superconducting phase. The similar behavior is reported by the phase diagram of the isomorph SrFe_2As_2 under P ¹⁵⁾ and the K-doped BaFe_2As_2 .¹⁶⁾ However, we again emphasize that, at the present stage, we cannot conclude that the anomaly below about 20-30 K is an intrinsic property of BaFe_2As_2 under P . We note that there is no clear change in spin-lattice relaxation time T_1 at 1.5 K between 0 and 2.49 GPa. If superconductivity sets in even at 2.49 GPa, we can expect the sufficient increase of T_1 due to the gap formation of superconductivity. This might indicate that the apparent superconductivity above 3 GPa is not a bulk superconductivity. The imperfection of the crystal possibly suppresses the superconductivity or the anomaly arises from a small amount of impurity phase consisting of Fe and As, which cannot be detected by NMR measurement. Therefore, we should continue the NMR measurements under P beyond 3 GPa in order to determine the magnetic phase diagram and ground state of BaFe_2As_2 under P with Bridgman anvil cell¹⁷⁾ and mini cubic anvil apparatus,¹⁸⁾ which are now in progress.

This work is supported by a Grant-in-Aid for Scientific Research from the MEXT.

- 1) Y. Kamihara *et al.*: J. Am. Chem. Soc. **130** (2008) 3296.
- 2) H. Kito *et al.*: J. Phys. Soc. Jpn. **77** (2008) 063707.
- 3) N. Takeshita *et al.*: J. Phys. Soc. Jpn. **77** (2008) 075003.
- 4) Z. A. Ren *et al.*: Euro. Phys. Lett. **82** (2008) 57002.
- 5) M. Rotter *et al.*: Phys. Rev. B **78** (2008) 020503(R).
- 6) Q. Huang *et al.*: arXiv:0806.2776v1.
- 7) M. Rotter *et al.*: arXiv:0805.4630v1.
- 8) P. L. Alireza *et al.*: arXiv:0807.1896v1.
- 9) H. Fukazawa *et al.*: to be published in J. Phys. Soc. Jpn. No.9 (2008); arXiv:0806.4514v3.
- 10) H. Fukazawa *et al.*: submitted to the Proceedings of the International Symposium on Fe-Oxipnictide Superconductors.
- 11) N. Móri *et al.*: High Pressure Research **24** (2004) 225.
- 12) Y. Tomioka: private communications.
- 13) H. Fukazawa *et al.*: J. Phys. Soc. Jpn. **76** (2007) 125001.
- 14) A.P. Reyes *et al.*: Rev. Sci. Instrum. **63** (1992) 3120.
- 15) M. Kumar *et al.*: arXiv: 0807.4283v1.
- 16) H. Chen *et al.*: arXiv: 0807.3950v1.
- 17) H. Fukazawa *et al.*: Rev. Sci. Instrum. **78** (2007) 015106.
- 18) K. Hirayama *et al.*: J. Phys. Soc. Jpn. **77** (2008) 075001.